

AD-A201 986

DTIC FILE COPY

4

OFFICE OF NAVAL RESEARCH

Contract N00014-80-K-0852

R&T Code \_\_\_\_\_

Technical Report No. 44

Utilization of a Hubbard U Model to Understand the Valence  
Band Photoelectron Data for the High-Temperature Superconductors

By

D. E. Ramaker

Prepared for Publication

in the

Physical Review B

George Washington University  
Department of Chemistry  
Washington, D.C. 20052

December, 1988

Reproduction in whole or in part is permitted for  
any purpose of the United States Government

This document has been approved for public release  
and sale; its distribution is unlimited.

DTIC  
ELECTE  
DEC 19 1988  
S H D

SECURITY CLASSIFICATION OF THIS PAGE

## REPORT DOCUMENTATION PAGE

1a. REPORT SECURITY CLASSIFICATION Unclassified			1b. RESTRICTIVE MARKINGS		
2a. SECURITY CLASSIFICATION AUTHORITY			3. DISTRIBUTION / AVAILABILITY OF REPORT Approved for Public Release, distribution Unlimited.		
2b. DECLASSIFICATION / DOWNGRADING SCHEDULE					
4. PERFORMING ORGANIZATION REPORT NUMBER(S) Technical Report # 44			5. MONITORING ORGANIZATION REPORT NUMBER(S)		
6a. NAME OF PERFORMING ORGANIZATION Dept. of Chemistry George Washington Univ.		6b. OFFICE SYMBOL (If applicable)	7a. NAME OF MONITORING ORGANIZATION Office of Naval Research (Code 413)		
6c. ADDRESS (City, State, and ZIP Code) Washington, D.C. 20052			7b. ADDRESS (City, State, and ZIP Code) Chemistry Program 800 N. Quincy Street Arlington, VA 22217		
8a. NAME OF FUNDING / SPONSORING ORGANIZATION Office of Naval Research		8b. OFFICE SYMBOL (If applicable)	9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER Contract N00014-80-K-0852		
8c. ADDRESS (City, State, and ZIP Code) Chemistry Program 800 North QUINCY, Arlington, VA 22217			10. SOURCE OF FUNDING NUMBERS		
			PROGRAM ELEMENT NO. 61153 N	PROJECT NO.	TASK NO. PP 013-08-01
			WORK UNIT ACCESSION NO NR 056-681		
11. TITLE (Include Security Classification) Utilization of a Hubbard U Model to Understand the Valence Band Photoelectron Data For the High Temperature Superconductors. (Uncl.)					
12. PERSONAL AUTHOR(S) D. E. Ramaker					
13a. TYPE OF REPORT Interim Technical		13b. TIME COVERED FROM TO		14. DATE OF REPORT (Year, Month, Day) December 1988	
15. PAGE COUNT 11					
16. SUPPLEMENTARY NOTATION Prepared for publication in Physical Review B					
17. COSATI CODES			18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)		
FIELD	GROUP	SUB-GROUP	Superconductivity, Photoelectron Spectroscopy, Hubbard Model, Electron Correlation. (jld)		
19. ABSTRACT (Continue on reverse if necessary and identify by block number)					
<p>The valence band photoelectron spectra are interpreted within a Hubbard model. The 9.5 eV "mystery" peak in the photoelectron spectra for <math>\text{YBa}_2\text{Cu}_3\text{O}_7</math> is identified as arising from a state with two holes localized on nearest neighbor oxygen atoms. Hubbard U parameters are obtained from the data and found to be larger than expected for metallic systems. Keywords:</p>					
20. DISTRIBUTION / AVAILABILITY OF ABSTRACT <input checked="" type="checkbox"/> UNCLASSIFIED/UNLIMITED <input checked="" type="checkbox"/> SAME AS RPT. <input type="checkbox"/> DTIC USERS			21. ABSTRACT SECURITY CLASSIFICATION Unclassified		
22a. NAME OF RESPONSIBLE INDIVIDUAL Dr. David L. Nelson			22b. TELEPHONE (Include Area Code) (202) 696-4410		22c. OFFICE SYMBOL

DD FORM 1473, 84 MAR

83 APR edition may be used until exhausted.  
All other editions are obsolete.SECURITY CLASSIFICATION OF THIS PAGE  
Unclassified

38 12 13 068

We interpret the valence band (VB) photoelectron spectra (UPS and XPS) for the high-temperature superconductors (HTSC's),  $\text{La}_{2-x}\text{Ba}_x\text{CuO}_4$  and  $\text{YBa}_2\text{Cu}_3\text{O}_7$  (herein referred to as La and 123). We identify the source of the "mystery" feature at 9.5 eV in the UPS [1], and explain the large differences seen between the calculated density of states (DOS) and the experimental spectra in the VB region [2].

The basic VB electronic structure of the HTSC's can be described by an extended Hubbard model, characterized by the transfer or hopping integral  $t$ , the Cu and O orbital energies  $\epsilon_d$  and  $\epsilon_p$ , the intra-site Coulomb repulsion energies  $U_d$  and  $U_p$ , and the inter-site repulsion energies  $U_{dp}$  and  $U_{pp}$  (i.e. between neighboring Cu-O and O-O atoms). The magnitudes of these  $U$  parameters are critical to the mechanism for the superconductivity. As a consequence, much effort has gone into theoretically calculating these parameters, but wide disagreement still exists over the magnitudes. Theoretical values for  $U_d$  in the range 6.5-10 eV,  $U_p$  (actually  $U_p - U_{pp}$ ) in the range 7-14 eV, and  $U_{dp}$  in the range 0.6-1.6 eV have been reported [3], with the smaller results favored based on the quality of the calculations. No results for  $U_{pp}$  have been reported. Our empirical results indicate that  $U_d = 9.5$ ,  $U_p = 12$ , and  $U_{pp} = 4.5$  eV for 123. The latter two are much larger than previously thought for these metallic systems, although  $U_p - U_{pp}$  is in agreement with the best theoretical results above.

We generalize the theory of vanderLaan et al [4] in an extended Hubbard model to interpret the spectra. All of the data can be understood within a  $\text{CuO}_4^{(2s-2p)}$  cluster model, which is valid when the  $U$ 's are large relative to the bandwidths [4], i.e. when correlation effects dominate covalent or hybridization effects. Both La and CuO contain  $\text{CuO}_4$  groups [5], having 4 short and 2 long Cu-O bonds. The 123 HTSC contains  $\text{CuO}_4$  and planar  $\text{CuO}_2$ .

groups [5]. The different  $n$  may alter the relative intensities of various features as pointed out below, but similar features are present in each case. The different bond lengths may increase the widths of the spectral features, but little else since correlation dominates.

The  $\text{CuO}_2^{(2x-2)-}$  cluster has one hole shared between the Cu 3d and O 2p shells in the ground state, which we term the  $v$  (valence) states. We indicate the location of the  $v$  hole by  $d$  (Cu 3d) or  $p$  (O 2p). In the case of two holes on the oxygens, we distinguish two holes on the same O ( $p^2$ ), on ortho neighboring O atoms ( $pp^o$ ), or on para O atoms ( $pp^p$ ) of the cluster. Furthermore, neighboring  $pp^o$  holes can dimerize [6], so we distinguish between two holes in bonded ( $pp^b$ ) and antibonded ( $pp^a$ ) O pairs.

Most of the O atoms actually participate in two  $\text{CuO}_2$  clusters. Consistent with previous work [7], we account for this by defining the effective parameter,  $c_p = c_p' + U_{pp}$ , where  $U_{pp}$  includes the interaction of a hole in an O  $p$  orbital with its environment. In general  $U_{pp}$  will be less than  $U_d$  due to polarization.

The  $v$  states, as reflected by the theoretical DOS [2], can be described as having the Cu-O bonding ( $t_b$ ) and antibonding ( $t_a$ ) orbitals centered at 4 and 0 eV and the nonbonding Cu and O orbitals at 2 eV. The O features each have a width  $2\Gamma = 4$  eV due to the O-O bonding and antibonding character and the Cu-O dispersion. The  $t_b$  and  $t_a$  wavefunctions can be expressed as [4],

$$t_b = d \cos\theta_1 - p \sin\theta_1 \quad (1a)$$

$$t_a = d \sin\theta_1 + p \cos\theta_1 \quad (1b)$$

where  $\theta_1 = 0.5 \tan^{-1}(2t/\Delta)$ . We also define the Cu-O hybridization shift  $\delta_1 = 0.5 \sqrt{\Delta^2 + 4t^2} - \Delta/2$ , which is utilized in Table 1 to give the energies. In this picture, the ground state of an average  $\text{CuO}_2$  cluster is located at 1 eV



codes  
avail and/or  
Special

0138

A-1

having the energy  $\epsilon_d - \delta + \Gamma/2 = \epsilon_d - \alpha$ , which we use as a reference energy for the  $v^2$  states. In CuO, the hybridization shift  $\Gamma$  is smaller, and we shall see below that  $\Delta\epsilon_p - \epsilon_d$  has increased to 1 eV. This increase can be attributed to an increase in  $\epsilon_p$ , or  $U_{pp}$ , and reflects a smaller lattice polarization response due to the more ionic character in CuO.

The photoemission process involves excitation from the ground  $v$  state (i.e. the  $\uparrow_d$  state) to the  $v^2$  states. Consistent with the final state rule [8], the photoelectron spectra reflect the  $v^2$  DOS, not the  $v$  DOS. In a highly correlated system, the  $v$  and  $v^2$  DOS are very different, explaining the well-known differences seen [2] between the theoretical DOS and the photoelectron spectra for the HTSC's.

Table 1 lists the 6 different  $v^2$  configurations. These configurations hybridize, i.e. 1,2,5 & 6 have the same symmetry and mix together to give  $\uparrow_a = \sum_i c_{ai} \phi_i$ . The coefficients  $c_{ai}$  are obtained by diagonalizing the 4x4 Hamiltonian matrix, assuming each of the 4 configurations ( $pp^0$ ,  $dp$ ,  $d^2$ , &  $p^2$ ) are orthogonal, and that  $pp^0$ ,  $p^2$ , and  $d^2$  have non-zero off-diagonal matrix elements with  $dp$  but zero with each other. The two  $pp^0$  states (3 & 4) have different symmetry and mix separately. The sudden approximation and the cross-sections for ionization from the O 2p and Cu 3d shells,  $\sigma_p$  and  $\sigma_d$ , can then be utilized to give the expected relative photoemission intensities,

$$I(m) = \sum_i (\langle \uparrow_a \psi_i | \uparrow_a \rangle)^2 \quad \sigma_i = \sum_i (\sum_a c_{ai} \langle \uparrow_a \psi_i | \phi_a \rangle)^2 \quad \sigma_i, \quad (2)$$

for the six  $v^2$  states. In eq. 2,  $\psi_i$  indicates the orbital of the hole created by the photoemission process, either d or p, where the new p hole may be created ortho, para or on the same O atom as the initial p hole, (i.e. to create the  $pp^0$ ,  $p^2$ , or  $pp^0$  configurations with relative cross-section  $\sigma_i = \sigma_p/n$ ,  $(n-2)\sigma_p/n$ , and  $\sigma_p/n$ , respectively).  $\sigma_p/\sigma_d$  is roughly 2. for 21 eV, 1. for 45, and 0.3 for 100 eV photons [2,9]. Results from eq. 2 utilizing the parameters

in Table 1 are given in Fig. 2. States 1 & 2 and 3 & 4 are heavily mixed so that they are the only ones to experience a significant hybridization shift,  $\delta_1$  and  $\Gamma$ , as shown in Table 1.

At low photon energies, the sudden approximation assumed above breaks down [10]. The opposite extreme, the adiabatic limit, gives intensity only in the lowest state of each symmetry, 1 and 3, since the system is able to relax before escape of the photoelectron. Since the relaxation time goes as the reciprocal of the shakeup energy [10], we expect that the high energy features, such as the  $d^2$  and  $p^2$  "satellites", will have much smaller intensity than that predicted by eq. 2.

The valence band features. Photon energy dependent data [11-13] in Figure 1 show that the VB features around 5.5 eV in CuO and 2.5 and 5 eV in 123 arise more from  $\sigma_p$ , and the feature at 3 in CuO and 4.2 eV in 123 from  $\sigma_d$  [13-15]. Based on our estimated energies, for CuO we assign the 5.5-eV feature to  $pp^*$ , and  $pp^*$  and the 3-eV to  $dp$ . In 123, we assign the 5-eV to  $pp^*$ , the 4.2 to  $dp$ , and the 2.5 to  $pp^*$ , where we indicate the dominant character of each hybridized state.

These assignments are also consistent with the results in Fig. 2. At low  $h\nu$  when  $\sigma_p$  dominates  $\sigma_d$ ,  $I(pp^*) + I(2)$  is about equal to  $I(1)$  at  $\Delta = 1$  in agreement with the data for CuO, while it is much greater than  $I(1)$  at  $\Delta = 0$  in agreement with the data for 123. At large  $h\nu$  when  $\sigma_d$  dominates  $\sigma_p$ ,  $I(1)$  and  $I(2)$  dominate. The calculated results in Fig. 2 indicate that  $I(1)/I(2)$  should equal about 1 at  $\Delta = 1$ , and about 0.5 at  $\Delta = 0$ , whereas the XPS results in Fig. 1 indicate that these ratios are qualitatively much larger. The enhancement of  $I(1)$  in both cases arises because of intensity transfer from the  $d^2$  state as a result of relaxation, which occurs even at XPS energies.

A character switch of state 1 from more  $dp$  to  $pp^*$  and vice versa for

state 2 between CuO and 123 arises because  $\Delta$  decreases from 1 eV to 0 eV. The smaller  $\Delta$  in 123, due to a smaller  $\epsilon_p$  or  $U_{pp}$ , is consistent with the Cu 2p XPS and XES data to be discussed elsewhere [16]. States 1 and 2 remain a few eV apart in spite of this switch because of the heavy CI mixing. Since state 1 is more of  $pp^*$  character in the SC's, the additional "charge carrier holes" (present in the La after Sr doping and in the 123 when  $7-x$  is greater than 6.5) are more on the oxygens.

Angle resolved PES data on single crystals of 123 show that the 2.5 eV feature is the only one which shows a small angular dispersion and a photon energy dependence [13]. The near lack of dispersion is consistent with our highly correlated cluster model. The small dispersion of the 2.5 eV feature probably comes from inter-CuO<sub>4</sub> cluster interaction, which is expected to be the largest when both holes are on the bordering O atoms.

The  $d^2$  satellite. The principal multiplet of the  $d^2$  final state for CuO is known to fall at 12.5 with a smaller one around 10 eV [11]. The intensity of the  $d^2$  final state is enhanced by the Cu 2p  $\rightarrow$  3d (or 2p  $\rightarrow$  4sp in Cu<sub>2</sub>O and Cu) resonant excitation process followed by an Auger decay [11]. This process is resonant between 72-80 eV. The SC's exhibit a behavior similar to CuO [14]. The satellites in Cu<sub>2</sub>O and Cu do not have non-resonant components [11] because the UPS for Cu<sub>2</sub>O and Cu reflect the one-hole DOS. However, the VB XPS of CuO and the HTSC's can and do show a significant nonresonant  $d^2$  satellite (see Figure 1) [17]; indeed, it should grow as one approaches the sudden limit. This possibility makes it even more difficult to interpret the data for the HTSC's, since the  $d^2$  satellite at 12.5 in the VB XPS falls at or near the same energy as the Ba spin-orbit split 5p features [1], which have been very controversial.

For the XPS (Figure 1a), Miller et al [1] have indicated that the 12.5 eV

feature results from the Ba representative of the bulk, and the 14 and 16 eV features result from Ba bonded to  $\text{OH}^-$  and  $\text{CO}_3^{2-}$  on the surface. Steiner et al [18] indicate that the 12.5 eV feature is representative of those Ba atoms surrounded by O atoms, but that the 14 and 16 eV features arise from those Ba atoms with either neighboring O defects or O atoms with holes (i.e.  $\text{O}^-$  instead of  $\text{O}_2^-$ ). Recent data [13] on single crystals cleaved in-situ (Fig. 1), when impurities are not expected, reveal only the 14 and 16 eV features at glancing emission (i.e. representative of the surface), and two additional features shifted up by about 1 eV at normal emission (i.e. more representative of the bulk). This shift has been interpreted as a surface chemical shift, but it is actually consistent with the Steiner data and interpretation, if one assumes more O defects exist at the surface than in the bulk. Recently Weaver et al [19] reported XPS data for sintered 123 which actually revealed only the features at 12.5 and 14 eV. This indicates either that their surfaces were free of impurities or that the bulk and surface were totally oxidized (i.e. within the Miller or Steiner interpretations). More experimental data is required here to conclusively decide on these two alternatives, but in our opinion the Steiner interpretation appears the more plausible at this time. Regardless of the interpretation, the intensity of the  $d^2$  feature is clearly much smaller than that predicted in Fig. 2 because of the relaxation to state 1. Theory indicates that  $I(d^2)$  should be smaller in 123 than in  $\text{CuO}$ , so the amount of the  $d^2$  satellite actually present in the XPS for the HTSC's is still uncertain.

The  $pp^*$  feature. The  $pp^*$  state is believed to be responsible for the "mystery" peak found at 9.5 eV in the UPS. Although initially it was thought to arise from carbon on the surface [20], more recent data [13, 21] (Fig. 1b) indicate that it is intrinsic to the material. Figure 1b indicates that such a



feature also appears for CuO [11,12]. This feature does not appear for Cu<sub>2</sub>O, as expected since UPS reflects the one-hole DOS in Cu<sub>2</sub>O. Thus this feature is not unique to the SC's; it naturally appears for those systems with two-hole photoemission final states.

The 9.5 eV feature has a cross-sectional dependence similar to  $\sigma_p$  [14,15], consistent with the  $pp^*$  identification. Figure 2 gives the combined intensity,  $I(pp^*) + I(pp^*)$ . We expect that  $I(pp^*)/I(pp^*)$  will be near 1 at XPS energies (this may also depend on the  $n$  in CuO<sub>2</sub>), and will be much smaller at UPS energies due to relaxation. Therefore  $I(pp^*)$  should decrease because of relaxation, but increase because of  $\sigma_p$  as  $h\nu$  decreases. A small contribution also exists from  $\sigma_s$  so that it is visible even at XPS energies. The data show that  $I(pp^*)$  is larger for 123 than for CuO and La. This is consistent with Fig. 2, and with the larger  $pp^*$  cross-section expected for smaller  $n$ .

An upper estimate of the two-center  $pp^*$  hole-hole repulsion,  $U_{pp^*}$ , can be obtained from the Klopman approximation [22],

$$U_{ij} = e^2/(r_{ij}^2 + (2e^2/(U_i + U_j))^2)^{1/2}, \quad (3)$$

where  $r_{ij}$  is the interatomic distance and  $U_i$  and  $U_j$  are the corresponding intra-atomic repulsion energies. Equation 2 gives a value for  $U_{pp^*}$  around 4.8 eV assuming  $r_{O-O}$  is 2.7 Å. The experimental energies of 9.5 and 5.0 eV for  $pp^*$  and  $pp^*$  in 123 suggests that the  $pp^*$  final state energy is 7.2 eV. This gives an empirical estimate for  $U_{pp^*}$  of 4.2 eV, very close to the Klopman theoretical result, which does not include the effects of interatomic screening.

The above result shows that metallic screening of two holes, which are spatially separated on neighboring O atoms, is not very significant. This is in contrast to two Cu-O holes, where Table 1 indicates the optimal  $U_{d^2}$  = 1 eV, while eq. 2 estimates  $U_{d^2}$  at 6.1 eV assuming  $r_{Cu-O}$  is 1.9 Å. This large

reduction in  $U_{d\sigma}$  may result from charge transfer into the Cu 4sp levels to screen the Cu-O holes. Although metallic screening, which results from virtual electron-hole (e-p) pair excitations at the Fermi level, is not expected to be large in an insulator such as CuO, screening effects are expected to be much larger in metals, such as the HTSC's. The above results show that  $U_{d\sigma}$  is significantly reduced in both, and  $U_{pp\sigma}$  remains large in both. The lack of a significant change in the U's between CuO and the HTSC's indicates that the DOS at the Fermi level in the HTSC's must be very small.

The assignment of the 9.5 eV feature explains some of its interesting characteristics. Comparison of data [14] for  $\text{YBa}_2\text{Cu}_3\text{O}_x$  (123<sub>x</sub>) with O levels at  $x = 6.95$ , 6.5, and 6.05 reveal that the reduced O materials, 123<sub>6.5</sub> and 123<sub>6.05</sub>, have two peaks around 9.4 and 11.5 eV. It is known that the oxygen decrease resulting from quenching or heating in vacuum occurs primarily from the  $\text{CuO}_4$  chains [23]. This may leave distorted  $\text{CuO}_4$  or even peroxide  $\text{O}_2^{2-}$  clusters [6] which have an O-O distance less than that in the ordered  $\text{CuO}_4$  groups, and hence a larger  $U_{pp\sigma}$ . A  $U_{pp\sigma}$  of 6.5 eV requires an O-O distance of less than 2 Å. Very recent data [24] on the new Bi and Th type HTSC's indicate a single feature around 10 eV similar to that for 123.

The  $p^2$  feature. Evidence for the existence of the  $p^2$  feature, estimated to appear at 17.5 eV for CuO can indeed be found around 17 eV in the XPS for CuO in Figure 1. UPS data for 123 [13] may reveal the  $p^2$  feature around 16 eV, moved up by at least 1 eV as predicted. Figure 1 shows UPS at  $h\nu = 100$  and 40 eV. The relative intensity of these two peaks changes when normally one would expect the relative intensity of the  $5p_{1/2}$  and  $5p_{3/2}$  peaks to remain constant with photon energy. But, the 40 eV spectrum should have a larger  $\sigma$ , contribution. This suggests that the  $h\nu = 40$  eV spectrum may have a contribution from the  $p^2$  state, such as that indicated in Figure 1.

Its intensity may arise as much from  $\sigma_4$  as from  $\sigma_6$  at large  $h\nu$ , although we indicate only the  $\sigma_6$  component in Fig. 2. Its theoretical intensity is remarkably independent of  $\Delta$ . At low  $h\nu$ , when  $\sigma_6$  dominates, its intensity remains small because of relaxation.

In summary, we have obtained a set of Hubbard parameters and derived intensity expressions which consistently predict the various features seen in the UPS data. The  $U$ 's involving the O atoms,  $U_p$  and  $U_{pp'}$ , are much larger in the metallic HTSC's than expected. We have assigned the UPS feature at 9.5 eV, and explained its characteristics. We will show elsewhere [16] that the Hubbard parameters determined here are consistent with core level XPS, x-ray emission and absorption, and Auger data.

TABLE 1 Summary of hole states revealed in the photoelectron data, and estimated energies using the following optimal values for the Hubbard parameters in eV<sup>a</sup>:

$$\begin{array}{llll} \delta_1 = 2 & c_4 = 2 & U_p = 12, 13 & U_d = 9.5, 10.2 \\ \delta_2 = 0.5, 0.8 & c_p = 2, 3 & U_{pp^*} = 4.5, 4 & U_{dp} = 1 \\ \Gamma = 2 & U_{pp^*} = 0. & \alpha = 1, 0.5 & \Delta = 0, 1. \end{array}$$

State <sup>b</sup>	Energy expression	Calc. E. eV <sup>c,d</sup>	Exp. E. eV <sup>c</sup>	Remark
<u>G.S. and IPES, v</u>				
+ <sub>a</sub> ) d	$c_d - \delta_1 \mp \Gamma$	0 $\mp$ 2	-	} heavily mixed
+ <sub>b</sub> ) p	$c_p + \delta_1 \mp \Gamma$	4 $\mp$ 2	-	
<u>UPS and XES, v<sup>1</sup></u>				
1) • pp <sup>*</sup>	$c_p + \Delta - \delta_2 + \alpha$	2.5	2.5	} heavily mixed
2) • dp	$c_p + U_{dp} + \delta_2 + \alpha$	4.5	4.2	
3) pp <sup>*</sup> <sub>a</sub>	$c_p + \Delta + U_{pp^*} - \Gamma + \alpha$	5.5	5.	} mystery peak Cu sat.
4) pp <sup>*</sup> <sub>b</sub>	$c_p + \Delta + U_{pp^*} + \Gamma + \alpha$	9.5	9.5	
5) d <sup>1</sup>	$c_d + U_d + \alpha$	12.5	12.5	
6) p <sup>1</sup>	$c_p + \Delta + U_p + \alpha$	15	16	

<sup>a</sup>Parameters for 123 indicated first, those for CuO second.

<sup>b</sup>The dominant character in the hybridized states is given.

<sup>c</sup>The Calc. E and Exp. E columns indicate the results for 123.

<sup>d</sup>The calculated E is defined relative to the ground v<sup>1</sup> (d) state energy =  $c_d - \alpha$ . The v<sup>1</sup>(d) energy defines the Fermi level relative to the vacuum level at zero.

<sup>e</sup>The dominant character switches as described in the text, and thus the sign in front of  $\delta_2$  is the opposite for CuO.

## References

\*Supported in part by the Office of Naval Research

1. D.C. Miller et al., in Thin Film Processing and Characterization of High Temperature Superconductors, J.M. Harper, J.H. Colton, and L.C. Feldman, Eds., AVS Series No. 3 (AIP: New York, 1988) p 336.
2. J. Redinger et al., Phys. Lett. 124, 463 (1987); 469 (1987).
3. C.F. Chen et al., unpublished; A.K. McMahan, R.M. Martin, and S. Satpathy, unpublished; M. Schluter, M.S. Hybertsen, and N. E. Christensen, Proc. Intn. Conf. High  $T_c$  Superconductors and Materials and Mechanisms of Superconductivity, J. Muller and J.L. Olsen, Eds., (Interlaken, Switzerland, 1988).
4. G. vanderLaan et al., Phys. Rev. 24, 4369 (1981); J.C. Fuggle et al., Phys. Rev. B37, 1123 (1988).
5. J.E. Greedan et al., Phys. Rev. B35, 8770 (1987).
6. R.A. de Groot et al, Sol. State Commun. 63, 451 (1987); W. Folkerts et al., J. Phys. C: Solid State Phys. 20, 4135 (1987); A. Manthiram et al., Phys. Rev. B37, 3734 (1988).
7. J.E. Hirsch et al., Phys. Rev. Letters 60, 1168 (1988).
8. D.E. Ramaker, Phys. Rev. B25, 7341, (1982).
9. M. Tang et al., Phys. Rev. B, accepted for publ.
10. J. W. Gadzuk and M. Sunjic, Phys. Rev. B12, 524 (1975).
11. M.R. Thuler, R.L. Benbow, and Z. Hurych, Phys. Rev. B26, 669 (1982).
12. C. Benndorf et al., J. Electron. Spectrosc. Related Phenom. 19, 77 (1980).
13. N.G. Stoffel et al., Phys. Rev. B37, 7952 (1988); B38, July (1988).
14. R. Kurtz et al., Phys. Rev. B35, 8818 (1987); D. Mueller et al., in Novel Mechanisms of Superconductors, S.A. Wolf and V.Z. Friesin, Eds., (Plenum: New York, 1987), p 829.

15. M. Tang et al., Phys. Rev. B37, 1611 (1988).
16. D.E. Ramaker, N.H. Turner, and F.L. Hutson, submitted.
17. A. Rosencwaig and G.K. Wertheim, J. Elect. Spectrosc. Related Phenom. 1, 493 (1972/73).
18. P. Steiner et al., Z. Phys. B - Condensed Matter 69, 449 (1988); Appl. Phys. A44, 75 (1987).
19. J. Weaver et al, preprint.
20. B. Reihl et al., Phys. Rev. B35, 8804 (1987).
21. A. Samsavar et al., Phys. Rev. B37, 5164 (1988).
22. G. Klopman, J. Am. Chem. Soc. 86, 4550 (1964).
23. J.H. Brewer et al., Phys. Rev. Lett. 60, 1073 (1988).
24. Y. Chang et al., preprint; M. Onellion et al., preprint.

### Figure Captions

Figure 1a) Comparison of photoelectron spectra in the range 10-18 eV for 123.

Data from refs. 13 ( $h\nu = 100$  and  $40$ ) and 1 ( $h\nu = 1487$ ).


1b) Comparison of UPS spectra for CuO and 123 taken with the

indicated photon energies in eV. Data for CuO from refs. 17 ( $h\nu =$


$1487$ ), 11 ( $h\nu = 74$ ) and 12 ( $h\nu = 21$ ). Data for 123 from ref. 13

( $h\nu = 25$  and  $74$ ) and 1 ( $h\nu = 1487$ ).

Figure 2) Calculated photoemission intensities for the  $v^+$  states obtained from evaluation of eq. 2, utilizing the parameters in Table 1 for  $\text{CuO}_4$  clusters. The intensities have been normalized so that the sum is  $\sigma_p + \sigma_d$ .

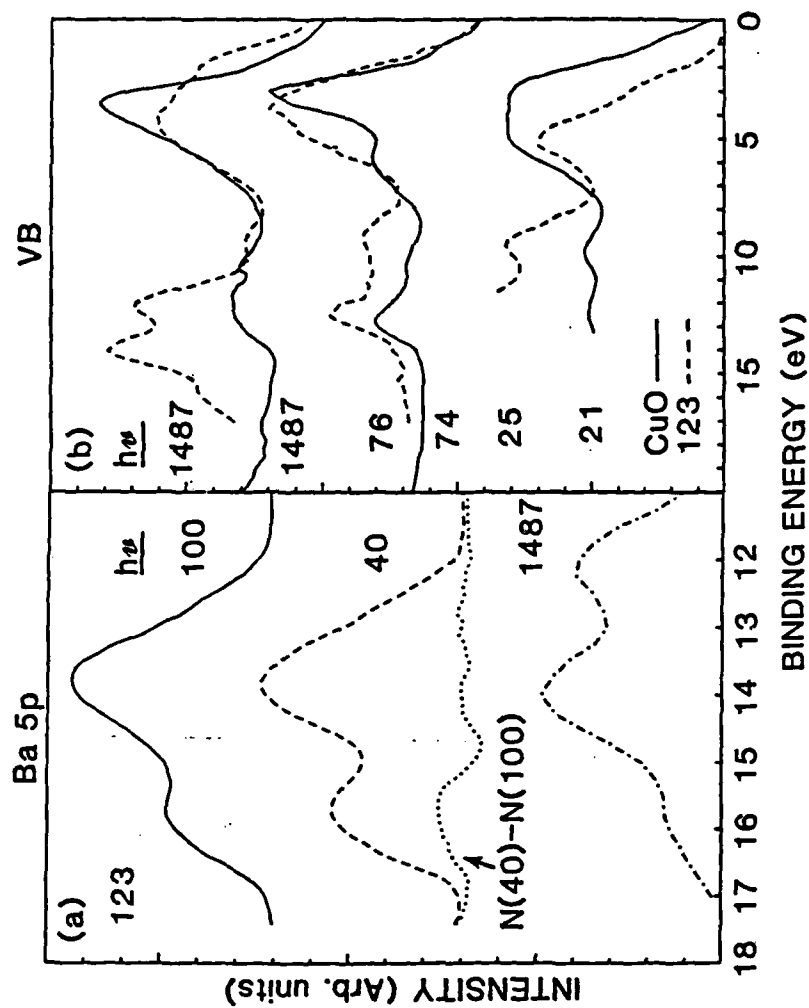



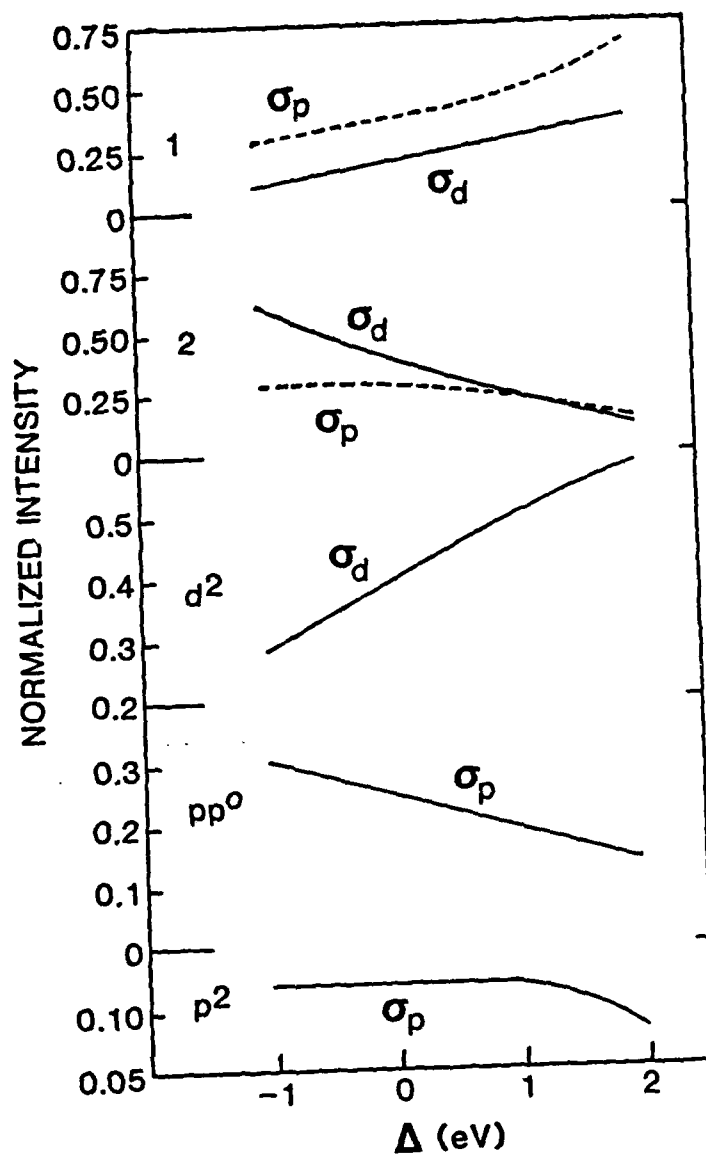

DL/1113/87/2

TECHNICAL REPORT DISTRIBUTION LIST, GEN

	<u>No. Copies</u>		<u>No. Copies</u>
Office of Naval Research Attn: Code 1113 800 N. Quincy Street Arlington, Virginia 22217-5000	2	Dr. David Young Code 334 NORDA NSTL, Mississippi 39529	1
Dr. Bernard Douda Naval Weapons Support Center Code 50C Crane, Indiana 47522-5050	1	Naval Weapons Center Attn: Dr. Ron Atkins Chemistry Division China Lake, California 93555	1
Naval Civil Engineering Laboratory Attn: Dr. R. W. Drisko, Code LS2 Port Hueneme, California 93401	1	Scientific Advisor Commandant of the Marine Corps Code RD-1 Washington, D.C. 20380	1
Defense Technical Information Center Building 5, Cameron Station Alexandria, Virginia 22314	12 high quality	U.S. Army Research Office Attn: CRD-AA-IP P.O. Box 12211 Research Triangle Park, NC 27709	1
DTNSRDC Attn: Dr. H. Singerman Applied Chemistry Division Annapolis, Maryland 21401	1	Mr. John Boyle Materials Branch Naval Ship Engineering Center Philadelphia, Pennsylvania 19112	1
Dr. William Tolles Superintendent Chemistry Division, Code 6100 Naval Research Laboratory Washington, D.C. 20375-5000	1	Naval Ocean Systems Center Attn: Dr. S. Yamamoto Marine Sciences Division San Diego, California 91232	1

ABSTRACTS DISTRIBUTION LIST, 056/625/629

Dr. F. Carter  
Code 6170  
Naval Research Laboratory  
Washington, D.C. 20375-5000

Dr. Richard Colton  
Code 6170  
Naval Research Laboratory  
Washington, D.C. 20375-5000

Dr. Dan Pierce  
National Bureau of Standards  
Optical Physics Division  
Washington, D.C. 20234

Dr. R. G. Wallis  
Department of Physics  
University of California  
Irvine, California 92664

Dr. D. Bamaker  
Chemistry Department  
George Washington University  
Washington, D.C. 20052

Dr. J. C. Hemminger  
Chemistry Department  
University of California  
Irvine, California 92717

Dr. T. F. George  
Chemistry Department  
University of Rochester  
Rochester, New York 14627

Dr. G. Rubloff  
IBM  
Thomas J. Watson Research Center  
P.O. Box 218  
Yorktown Heights, New York 10598

Dr. J. Baldeschwieler  
Department of Chemistry and  
Chemical Engineering  
California Institute of Technology  
Pasadena, California 91125

Dr. Galen D. Stucky  
Chemistry Department  
University of California  
Santa Barbara, CA 93106

Dr. A. Steckl  
Department of Electrical and  
Systems Engineering  
Rensselaer Polytechnic Institute  
Troy, New York 12181

Dr. John T. Yates  
Department of Chemistry  
University of Pittsburgh  
Pittsburgh, Pennsylvania 15260

Dr. R. Stanley Williams  
Department of Chemistry  
University of California  
Los Angeles, California 90024

Dr. R. P. Messmer  
Materials Characterization Lab.  
General Electric Company  
Schenectady, New York 12217

Dr. J. T. Keiser  
Department of Chemistry  
University of Richmond  
Richmond, Virginia 23173

Dr. R. W. Plummer  
Department of Physics  
University of Pennsylvania  
Philadelphia, Pennsylvania 19104

Dr. E. Yeager  
Department of Chemistry  
Case Western Reserve University  
Cleveland, Ohio 44106

Dr. N. Winograd  
Department of Chemistry  
Pennsylvania State University  
University Park, Pennsylvania 16802

Dr. Roald Hoffmann  
Department of Chemistry  
Cornell University  
Ithaca, New York 14853

Dr. Robert L. Whetten  
Department of Chemistry  
University of California  
Los Angeles, CA 90024

Dr. Daniel M. Neumark  
Department of Chemistry  
University of California  
Berkeley, CA 94720

Dr. G. H. Morrison  
Department of Chemistry  
Cornell University  
Ithaca, New York 14853

ABSTRACTS DISTRIBUTION LIST, 056/625/629

Dr. J. E. Jensen  
Hughes Research Laboratory  
3011 Malibu Canyon Road -  
Malibu, California 90265

Dr. J. H. Weaver  
Department of Chemical Engineering  
and Materials Science  
University of Minnesota  
Minneapolis, Minnesota 55455

Dr. A. Reisman  
Microelectronics Center of North Carolina  
Research Triangle Park, North Carolina  
27709

Dr. M. Grunze  
Laboratory for Surface Science  
and Technology  
University of Maine  
Orono, Maine 04469

Dr. J. Butler  
Naval Research Laboratory  
Code 6115  
Washington D.C. 20375-5000

Dr. L. Interante  
Chemistry Department  
Rensselaer Polytechnic Institute  
Troy, New York 12181

Dr. Irvin Heard  
Chemistry and Physics Department  
Lincoln University  
Lincoln University, Pennsylvania 19352

Dr. K. J. Klaubunde  
Department of Chemistry  
Kansas State University  
Manhattan, Kansas 66506

Dr. C. B. Harris  
Department of Chemistry  
University of California  
Berkeley, California 94720

Dr. R. Bruce King  
Department of Chemistry  
University of Georgia  
Athens, Georgia 30602

Dr. R. Reeves  
Chemistry Department  
Rensselaer Polytechnic Institute  
Troy, New York 12181

Dr. Steven M. George  
Stanford University  
Department of Chemistry  
Stanford, CA 94305

Dr. Mark Johnson  
Yale University  
Department of Chemistry  
New Haven, CT 06511-8118

Dr. W. Knauer  
Hughes Research Laboratory  
3011 Malibu Canyon Road  
Malibu, California 90265

Dr. Theodore E. Madey  
Surface Chemistry Section  
Department of Commerce  
National Bureau of Standards  
Washington, D.C. 20234

Dr. J. E. Demuth  
IBM Corporation  
Thomas J. Watson Research Center  
P.O. Box 218  
Yorktown Heights, New York 10598

Dr. M. G. Lagally  
Department of Metallurgical  
and Mining Engineering  
University of Wisconsin  
Madison, Wisconsin 53706

Dr. R. P. Van Duyne  
Chemistry Department  
Northwestern University  
Evanston, Illinois 60637

Dr. J. M. White  
Department of Chemistry  
University of Texas  
Austin, Texas 78712

Dr. Richard J. Saykally  
Department of Chemistry  
University of California  
Berkeley, California 94720

ABSTRACTS DISTRIBUTION LIST, 056/625/629

Dr. G. A. Somorjai  
Department of Chemistry  
University of California  
Berkeley, California 94720

Dr. J. Murday  
Naval Research Laboratory  
Code 6170  
Washington, D.C. 20375-5000

Dr. W. T. Peria  
Electrical Engineering Department  
University of Minnesota  
Minneapolis, Minnesota 55455

Dr. Keith H. Johnson  
Department of Metallurgy and  
Materials Science  
Massachusetts Institute of Technology  
Cambridge, Massachusetts 02139

Dr. S. Sibener  
Department of Chemistry  
James Franck Institute  
5640 Ellis Avenue  
Chicago, Illinois 60637

Dr. Arold Green  
Quantum Surface Dynamics Branch  
Code 3817  
Naval Weapons Center  
China Lake, California 93555

Dr. A. Wold  
Department of Chemistry  
Brown University  
Providence, Rhode Island 02912

Dr. S. L. Bernasek  
Department of Chemistry  
Princeton University  
Princeton, New Jersey 08544

Dr. W. Kohn  
Department of Physics  
University of California, San Diego  
La Jolla, California 92037

Dr. Stephen D. Kevan  
Physics Department  
University Of Oregon  
Eugene, Oregon 97403

Dr. David M. Walba  
Department of Chemistry  
University of Colorado  
Boulder, CO 80309-0215

Dr. L. Kesmodel  
Department of Physics  
Indiana University  
Bloomington, Indiana 47403

Dr. K. C. Janda  
University of Pittsburg  
Chemistry Building  
Pittsburg, PA 15260

Dr. E. A. Irene  
Department of Chemistry  
University of North Carolina  
Chapel Hill, North Carolina 27514

Dr. Adam Heller  
Bell Laboratories  
Murray Hill, New Jersey 07974

Dr. Martin Fleischmann  
Department of Chemistry  
University of Southampton  
Southampton SO9 5NH  
UNITED KINGDOM

Dr. H. Tachikawa  
Chemistry Department  
Jackson State University  
Jackson, Mississippi 39217

Dr. John W. Wilkins  
Cornell University  
Laboratory of Atomic and  
Solid State Physics  
Ithaca, New York 14853

Dr. Ronald Lee  
R301  
Naval Surface Weapons Center  
White Oak  
Silver Spring, Maryland 20910

Dr. Robert Gomer  
Department of Chemistry  
James Franck Institute  
5640 Ellis Avenue  
Chicago, Illinois 60637

Dr. Horia Metiu  
Chemistry Department  
University of California  
Santa Barbara, California 93106

Dr. W. Goddard  
Department of Chemistry and Chemical  
Engineering  
California Institute of Technology  
Pasadena, California 91125